Impairment of double exchange mechanism in electron transport of iron pnictides

Lei Hao, Chi-Cheng Lee, and T. K. Lee
Institute of Physics, Academia Sinica, Nankang, Taipei 11529, Taiwan
(Dated: July 12, 2011)

Double exchange mechanism is believed to favor transport along ferromagnetic directions, the failure of which in explaining the unusual resistivity anisotropy in iron pnictides is investigated. Several factors intrinsic to the microscopic mechanism of transport in iron pnictides are identified and analyzed, including the moderate Hund's coupling, low local moment, and presence of two anisotropic degenerate orbitals xz and yz. In particular, the substantial second neighbor hoppings are found to be decisive in giving results opposite to the double exchange picture. In high temperature nonmagnetic phase, orbital ordering is shown to give the right trend of resistivity anisotropy as observed experimentally, advocating its essential role in electron transport of iron pnictides.

PACS numbers: 74.70.Xa, 74.25.F-, 75.30.Mb, 75.25.Dk

arXiv:1107.1952v1 [cond-mat.mtrl-sci] 11 Jul 2011

Close interplay among spin, orbital, and lattice degrees of freedom together with the high-temperature superconductivity make iron pnictides a rich playground to study the effects of electron correlations. Unlike cuprates and manganites, all families of iron pnictides are metallic without doping. This greatly interests researchers in studying the transport property under different circumstances and studying its relationship to all kinds of degrees of freedom [1–8]. Recently, an unusual resistivity anisotropy was observed in detwined underdoped $Ba(Fe_{1-x}Co_x)_2As_2$ [1–6] and was confirmed in other iron pnictides [7, 8]. The low temperature normal state of the material is an antiferromagnetic (AF) metal with collinear $(\pi, 0)$ ordering. Experimentally, the resistivity was found to be larger along the ferromagnetic (F) direction than along the AF direction. This is thought to be in direct contradiction to at least two reasonings: (1) The ferromagnetic Hund's coupling between local moments and the itinerant electrons indicates a double exchange (DE) like correlation between spin configuration and transport, which implies a lower resistivity along the F direction [1, 9]. (2) The scattering rate is expected to be larger along the AF direction [10], which is confirmed in optical conductivity experiment [4, 11]. Another surprising result is that the resistivity anisotropy is largest close to the border between the AF phase and the superconducting dome, where the magnetism and structural distortion are weaker [1].

Though conceptually puzzling, the early experimental results mentioned above are reproduced by several theoretical calculations, including both mean field studies [10, 12, 13] and other more advanced techniques such as the dynamical mean field theory [14–16]. Nevertheless, a clear physical picture concerning why the DE mechanism not working has not been addressed. Current understanding of mean field results on resistivity anisotropy is only based on the topology and morphology of the Fermi surface [10], leaving the underlying mechanism untold. The failure of the interplay between ferromagnetism and conductivity in the AF metallic phase is thus hazy and still remains a puzzle. If the scattering rate is indeed stronger along the AF direction helping the electron transport along F direction [4], there must be a non-negligible competitor making the DE mechanism much less effective. Since several calculations via different methods all observe this same unusual resistivity anisotropy, the underlying physics should be simple. It is thus interesting and timely to explore the applicability of the DE mechanism in iron pnictides, especially because the DE based model itself has been used successfully to unify the magnetic correlations in iron-based superconductors [17] and account for the novel spin dynamics [18]. Besides, the reason of impairment of double exchange mechanism in transport may also happen in other materials. In addition, orbital ordering is known to play an important role in many aspects of the system [19–22]. Surprisingly, mean field calculations have shown that orbital ordering is irrelevant to [12] or even give opposite trend compared to [10] the experimental results. It is extremely desirable to reexamine the correlation between orbital ordering and the resistivity anisotropy presently.

In this Letter, we report a theoretical study on the applicability of DE mechanism in the electron transport of iron pnictides. A so-called orbital-degenerate DE model [17, 18] is used to uncover the underlying mechanism of resistivity anisotropy both below and slightly above the structural and magnetic phase-transition temperatures. Although the DE effect is already weaken by the small Hund's coupling, low local moments and two degenerate anisotropic orbitals, the relation between magnetism and transport anisotropy is still expected to follow the DE idea. The *substantial second-neighbor hoppings* are found to give rise to both a gapping feature in the band structure and a frustration in kinetic energy gain in transport along the F direction in the AF phase and is identified as an important factor in competition with the DE mechanism. In the high-temperature nonmagnetic phase, the orbital ordering that could arise from a tiny external stress is shown to give the right trend of resistivity anisotropy and thus contributes positively to the experi-

mental resistivity anisotropy.

The model H=H_0+H_K+H_S+H_L contains four terms. H_0 is the tight binding term up to second neighbor hopping [17, 23]. H_K is the local Hund's coupling between localized spin and the itinerant electron spin, and is defined as H_K=$-\frac{1}{2}K\sum_{\mathbf{i},\mu,\alpha,\beta}\mathbf{S_i}\cdot(d^\dagger_{\mathbf{i},\mu,\alpha}\boldsymbol{\sigma}_{\alpha\beta}d_{\mathbf{i},\mu,\beta})$. μ indicates the orbital index. K>0 is the strength of Hund's coupling, σ_i is the i-th Pauli's matrix acting in the spin subspace, and $\mathbf{S_i}$ is the localized spin on site $\mathbf{i}$. In order to maximize the DE mechanism, we take $\mathbf{S_i}$ as classical spins [17]. Since we focus on the $\mathbf{Q}$=$(\pi,0)$ AF phase, we can take $\mathbf{S_i}$=$S\hat{z}\cos(\mathbf{Q}\cdot\mathbf{R_i})$. In the following, we redefine J=$KS/2$ to measure the strength of Hund's coupling. The first two terms of the model constitute the DE model in the limit of large Hund's coupling, which is well-known to facilitate transport along F directions[24, 25].

H_S is the superexchange term between localized spins, which competes with the first two terms to determine the ground state magnetic order and spin dynamics [17, 18]. Since we concentrate on the electron transport in the fixed $\mathbf{Q}=(\pi,0)$ AF phase in this work, H_S is neglected in what follows. The final term is a crystal field splitting between the two orbitals as a result of the external stress field. It is written as $H_L=\frac{1}{2}\Delta\sum_{\mathbf{i}}(n_{\mathbf{i},1}-n_{\mathbf{i},2})$, where $n_{\mathbf{i},\mu}$=$\sum_\sigma d^\dagger_{\mathbf{i},\mu,\sigma}d_{\mathbf{i},\mu,\sigma}$ is the number operator for electrons in orbital μ and on site $\mathbf{i}$. The lattice distortion also changes the hopping amplitudes along x and y directions [26]. However, we consider this as a minor effect in our present system of undoped or underdoped iron pnictides and neglect it in the following analyses.

In the $(\pi,0)$ AF phase, every unit cell contains two irons. Relabeling the electron annihilation operators on the two sublattices as $a_{\mathbf{k},\mu,\sigma}$ and $b_{\mathbf{k},\mu,\sigma}$. Take the σ spin basis as $\psi^\dagger_{\mathbf{k}\sigma}$=$\{a^\dagger_{\mathbf{k},1,\sigma},b^\dagger_{\mathbf{k},1,\sigma},a^\dagger_{\mathbf{k},2,\sigma},b^\dagger_{\mathbf{k},2,\sigma}\}$. Ignoring H_S, the original model is written as H=$H_0+H_K+H_L$=$\sum_{\mathbf{k}\sigma}\psi^\dagger_{\mathbf{k}\sigma}h^\sigma_{\mathbf{k}}\psi_{\mathbf{k}\sigma}$, where

$$h^\sigma_{\mathbf{k}}=\begin{pmatrix} f^\sigma_{1a}(\mathbf{k}) & f_3(\mathbf{k}) & 0 & f_5(\mathbf{k}) \\ f_3(\mathbf{k}) & f^\sigma_{1b}(\mathbf{k}) & f_5(\mathbf{k}) & 0 \\ 0 & f_5(\mathbf{k}) & f^\sigma_{2a}(\mathbf{k}) & f_4(\mathbf{k}) \\ f_5(\mathbf{k}) & 0 & f_4(\mathbf{k}) & f^\sigma_{2b}(\mathbf{k}) \end{pmatrix}, \quad (1)$$

in which $f^\sigma_{1a}(\mathbf{k})=-2t_1\cos(k_yc_2)+\frac{\Delta}{2}-\sigma J$, $f^\sigma_{1b}(\mathbf{k})=-2t_1\cos(k_yc_2)+\frac{\Delta}{2}+\sigma J$, $f^\sigma_{2a}(\mathbf{k})=-2t_2\cos(k_yc_2)-\frac{\Delta}{2}-\sigma J$, $f^\sigma_{2b}(\mathbf{k})=-2t_2\cos(k_yc_2)-\frac{\Delta}{2}+\sigma J$, $f_3(\mathbf{k})=-2t_2\cos(k_xc_1)-4t_3\cos(k_xc_1)\cos(k_yc_2)$, $f_4(\mathbf{k})=-2t_1\cos(k_xc_1)-4t_3\cos(k_xc_1)\cos(k_yc_2)$, $f_5(\mathbf{k})=-4t_4\sin(k_xc_1)\sin(k_yc_2)$. c_1 (c_2) is lattice constant along x (y). Along (k_x, 0) or (0, k_y), $f_5(\mathbf{k})$=0, the two eigenenergies for the two orbitals are written compactly as

$$\lambda_{\mu,\pm}=-2t_\mu\cos(k_yc_2)-(-1)^\mu\frac{\Delta}{2}\pm\sqrt{J^2+f^2_{\mu+2}(\mathbf{k})}, \quad (2)$$

with $\mu=1$ ($\mu=2$) for the xz (yz) orbital. From the above expression, the two orbitals open gaps both along the k_x and the k_y directions. Along k_x, the positions of gap opening of the two orbitals are far away from each other by a distance of $|2(t_1-t_2)-\Delta|$. For experimentally realistic J, no full gap opens along k_x, which is consistent with a topological argument by Ran *et al* [27]. This Dirac cone structure appears along k_x as an accidental crossing of the energy bands corresponding separately to the two orbitals. However, it could be proved that for Δ=0 and small J the gap positions for the two orbitals always coincide with each other along k_y and are centered around t_1t_2/t_3. This orbital-cooperated gap would highly enhance the corresponding resistivity.

For the hopping integrals, we consider mainly the parameters proposed by Raghu *et al* [23] and fix the largest hopping integral as t_1=0.4 eV [17, 19]. The ratios among the four hopping integrals t_1:t_2:t_3:t_4 are 1.3:(-1):(-0.85):(-0.85). Results for another set of parameters used by Yin *et al* [17], in which t_1:t_2:t_3:t_4=4:1.3:(-2.5):0.7, are found to give qualitatively the same results. These two sets of parameters agree qualitatively in the sense that the nearest neighbor intra-orbital hopping integral of the xz (yz) orbital along the y (x) direction t_1 is larger than along the x (y) direction t_2, a peculiar feature resulting from the strong hybridization of the iron orbitals with the p orbitals of surrounding As ions [19].

The DE mechanism, first introduced for manganites, applies when the ferromagnetic Hund's coupling J is much larger than the hopping amplitudes and for a partly filled band [24, 25]. Though the Hund's coupling for iron pnictides is not as large, it is not obvious why a result opposite to expectation based on DE is observed. To have a feeling on the global behavior of the model, we show in Fig. 1(a) the resistivity ratio ρ_y/ρ_x in a wide range of J, at 50 K in the low temperature AF phase. Two electrons per iron is considered for the undoped system [23, 28, 29]. The finite temperature resistivity (conductivity) is obtained from standard Kubo's formula [30]. For low J the resistivity anisotropy agrees with experiments. But when J increases to an unphysical value for iron pnictides, the resistivity anisotropy changes to the opposite behavior as compared to experiment, which is however in agreement with expectation from the DE mechanism. One peculiar feature on Fig. 1(a) is for very large J the resistivity anisotropy of the undoped system changes back to the behavior same as in experiment, a result specific to the undoped and extremely low doped systems and easily understood from the Pauli's exclusion principle for electrons in a half filled band.

Before answering the question why undoped and slightly electron doped iron pnictides behave differently from DE predictions, we first calculate the resistivity anisotropy for a single orbital model with isotropic in-plane hoppings up to nearest neighbor, that is to set $t_1=t_2$ and $t_3=t_4=0$. The results show that even for extremely small J, the resistivity is smaller along the F direction, following exactly the DE prediction [24, 25]. Thus, the small magnitude of J is not the crucial factor

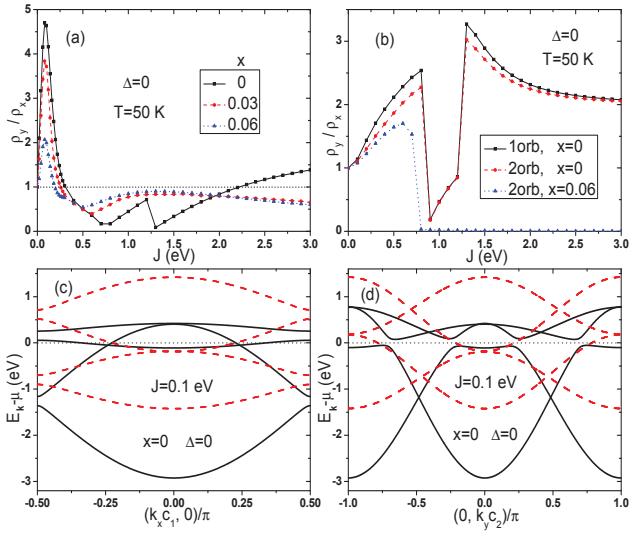

FIG. 1: (a) Ratio of resistivity as a function of J between ρ_y along the F direction and ρ_x along the AF direction, for three typical dopings at 50K. (b) ρ_y/ρ_x for isotropic one orbital (labeled as '1orb') and two orbital (labeled as '2orb') models with 2NN hopping, at 50 K. (c) and (d) are dispersions along k_x and k_y for $J = 0.1$ eV both in the presence (solid lines) and absence (dashed lines) of 2NN hoppings, respectively. The horizontal dotted lines in (c) and (d) mark the chemical potential.

to bring about the observed anisotropy.

However, the inclusion of substantial second nearest neighbor (2NN) hoppings in combination with the small magnitude of J literally induces the unusual resistivity anisotropy in iron pnictides, which is further enhanced by the large anisotropy in the intraorbital nearest neighbor (NN) hoppings. To see the effect of 2NN hoppings, we show in Fig. 1(b) the resistivity anisotropy for a model with one isotropic orbital (t_2=t_1=0.4 eV, t_3=-0.25 eV, t_4=0) and two isotropic orbitals (t_2=t_1=0.4 eV, t_3=-0.25 eV, t_4=0.07 eV). Though with very different line shapes, the same qualitative behavior as in Fig. 1(a) is obtained. From Fig. 1(b), it is also obvious that a nonzero 2NN inter-orbital hopping t_4 tends to reduce the magnitude of the resistivity anisotropy.

To understand the role played by 2NN hoppings, first notice that in a square lattice the effective hopping along each of the two in-plane directions have contributions from both the NN and the 2NN hoppings. In the $(\pi, 0)$ AF phase, the NN and 2NN hoppings along x both connect AF bonds while they connect F and AF bonds respectively along y. When J is very large, the 2NN hoppings together with the NN hoppings along the AF direction are effectively blocked, the DE mechanism simply prevails. However, in the region of small J, a more intricate competition between the maximization of kinetic energy gain and minimization of Hund's energy appears. Since hopping along the F bonds does not cost or gain magnetic energy, maximization of kinetic energy gain for $J \ll t_1$ prefers a nearly non-polarized on-site spin distribution. Whereas along the AF direction, the up and down spin electrons each experiences effectively a periodic shallow potential wells of depth $2J$, both of two-site period and shifted from each other by one site. This pair of periodic potential wells tends to drive the formation of notable local spin polarizations, which can lower the Hund's energy at the cost of kinetic energy loss. Since for small J the kinetic energy gain is dominant, for negligible 2NN hoppings the spin polarization follows largely that of the F direction. However, the additional magnetic energy gain from hoppings along AF 2NN bonds enhances the spin polarization, as verified through explicit calculations. This in turn frustrates hopping along the F bonds and finally impairs the DE for large enough t_3. We believe that the above is the physical picture why substantial 2NN hoppings *invalidate* the DE mechanism for very small J.

The effect of the 2NN hoppings could be further understood from the band structure. For clarity, the band structures for $J = 0.1$ eV in the presence and absence of the 2NN hoppings are shown together by solid and dashed lines in Figs. 1(c) (1(d)) along k_x (k_y). In the absence of 2NN hoppings, the energy bands are more metallic along k_y than along k_x since no energy gap opens in the whole energy range in the former. When the 2NN hoppings are turned on, the band structures for undoped and slightly doped systems would be gapless along k_x but would open a gap along k_y as we have mentioned following Eq.(2). This peculiar change in the direction of gap opening tendency follows exactly the change from DE behavior to anti-DE behavior and thus provides a very clear picture how 2NN hoppings invalidate DE. The gap along k_y exists once $|t_3/t_1| \geq 1/2$, providing a good reference critical value for the 2NN hoppings.

Another important feature of iron pnictides different from standard DE systems (e.g., manganites) is that the two relevant orbitals are anisotropic with respect to x and y, which is manifested through $|t_1/t_2| > 1$. Comparing Fig. 1(a) and Fig. 1(b), this intrinsic anisotropy enhances the resistivity anisotropy and gives rise to the peak structure in the small J region on Fig. 1(a). The low J peak is far less obvious in the absence of this anisotropy, as could be seen from Fig. 1(b).

Former mean field calculations found smaller resistivity anisotropy for high moment states than for low moment states [10, 12]. According to Fig. 1(a), the reduction of resistivity anisotropy in the high moment phase indicates that iron pnictides should belong to the region changing from anti-DE behavior to DE behavior. We notice that there are iron based superconductors which are considered as having larger effective J, such as $FeTe_{1-x}Se_x$ [17]. One prediction worthy of future experimental inspection is that opposite resistivity anisotropy with larger resistivity along the AF direction in the un-

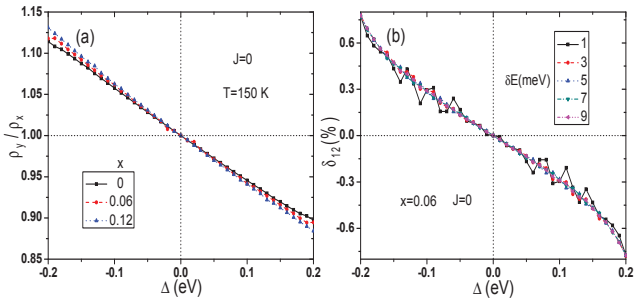

FIG. 2: (a) Ratio of resistivity between the direction with short lattice constant (ρ_y) and the direction with long lattice constant (ρ_x), for three typical dopings. Temperature is taken as 150K, without of magnetization. (b) The orbital polarization δ_{12} (in percentage) close to the chemical potential for a series of increasing energy windows δE.

derdoped region of these materials might be observed.

One common feature in iron pnictides is that a structural transition always occurs at a higher or the same temperature as compared with the AF transition [1], in which the orbital ordering and fluctuations are considered by many to be essential [19–21]. It is thus very surprising that former mean-field studies showed that orbital ordering is anti-correlated with the resistivity anisotropy in the AF phase [10, 12]. Experimentally, the same resistivity anisotropy is observed in the high temperature nonmagnetic phase close to the AF and structural transition when an external stress field is applied to induce a lattice distortion following the structural anisotropy in the AF phase [1]. Here we would like to single out the role played by the orbital ordering in this phase. In the low doping region, we expect crystal field effect to be dominant, and consider a dominance of the xz orbital for a lattice with a larger lattice constant along x, implying $\Delta < 0$ in our model [26]. As shown in Fig. 2(a), orbital ordering gives the *right* trend of resistivity anisotropy compared to experiment. We then calculate the orbital polarization for states close to the chemical potential, which are most relevant to electron transport, for a typical doping and a series of increasing energy windows δE in Fig. 2(b). Denoting the integrated density of states of xz (yz) orbital within δE as δn_1 (δn_2), the orbital polarization δ_{12} is defined as $(\delta n_1 - \delta n_2)/(\delta n_1 + \delta n_2)$. It is clear that δ_{12} close to the chemical potential has the same character as the total orbital polarization set by the sign of Δ. Note that fluctuations via nematic correlations [1, 15] neglected here might be important to provide a complete picture for the high temperature resistivity anisotropy and deserves future investigations.

The above correlation between orbital polarization and resistivity anisotropy is encoded in the intrinsic anisotropy of the two degenerate orbitals. As could be seen from Eq.(1) for $J = 0$, the effective intraorbital hopping along k_x is $-2(t_2+2t_3)\cos(k_x c)$ for xz orbital and is $-2(t_1+2t_3)\cos(k_x c)$ for yz orbital [23]. For both of two parameter sets considered, $|t_1 + 2t_3| < |t_2 + 2t_3|$ [17, 23]. So in a qualitative sense, a dominant xz polarization close to the chemical potential implies an easier hopping and conduction along x direction. In comparison, yz has a larger effective hopping along the y direction and thus facilitates the conduction along y direction.

In conclusion, the puzzling interplay between magnetic order and electron transport in iron pnictides is identified quite different from DE-dominated systems (e.g., manganites). The small Hund's coupling, low local moments and intrinsic anisotropy in the NN hoppings all make the DE a bad description. In particular, the substantial 2NN hoppings are found to be decisive in competing with the DE mechanism, greatly frustrating the kinetic energy gain in transport along the ferromagnetic direction. We have also found in the high temperature nonmagnetic phase that, an xz dominated polarization which might arise as a result of an external stress could give the same trend of resistivity anisotropy as observed in experiments, advocating the possible essential role of orbital ordering in the resistivity anisotropy.

We reemphasize that $|t_3/t_1| \sim 0.5$ is a good reference critical value of the 2NN intra-orbital hopping to impair the DE mechanism (for small J), the exact value of which depends on t_4 and J. First-principles 2NN hoppings for all three t_{2g} (two e_g) orbitals are larger (smaller) than half of the corresponding NN hoppings [19]. Since the Fermi surface of iron pnictides are dominated by t_{2g} orbitals, a model containing more orbitals should not change our previous arguments. Similar impairment of the DE mechanism might be observed in other t_{2g}-dominated systems [31]. $SrCrO_3$ is also an AF metal with (π, π, 0) magnetic order similar to iron pnictides [32]. However, our first-principles calculations give 2NN hoppings smaller than half of NN hoppings for all five orbitals, predicting that DE should persist in that system. This work was supported by the NSC Grant No. 98-2112-M-001-017-MY3. Part of the calculations was performed in the National Center for High-Performance Computing in Taiwan.

[1] J.-H. Chu *et al.*, Science **329**, 824 (2010).
[2] M. A. Tanatar *et al.*, Phys. Rev. B **81**, 184508 (2010).
[3] Ming Yi *et al.*, PNAS 1015572108 (2011).
[4] A. Dusza *et al.*, Euro. Phys. Lett. **93**, 37002 (2011).
[5] J. J. Ying *et al.*, arXiv:1012.2731.
[6] Hsueh-Hui Kuo *et al.*, arXiv:1103.4535.
[7] E. C. Blomberg *et al.*, Phys. Rev. B **83**, 134505 (2011).
[8] I. R. Fisher *et al.*, arXiv:1106.1675.
[9] Ari M. Turner *et al.*, Phys. Rev. B **80**, 224504 (2009).
[10] B. Valenzuela *et al.*, Phys. Rev. Lett. **105**, 207202 (2010).
[11] A. Sanna *et al.*, Phys. Rev. B **83**, 054502 (2011).
[12] K. Sugimoto *et al.*, J. Phys. Soc. Jpn. **80**, 033706 (2011).
[13] Weicheng Lv and Philip Phillips, arXiv:1105.4630.

[14] Z. P. Yin *et al.*, arXiv:1007.2867.
[15] M. S. Laad and L. Craco, arXiv:1010.2940v1.
[16] Rafael M. Fernandes *et al.*, arXiv:1105.3906.
[17] Wei-Guo Yin *et al.*, Phys. Rev. Lett. **105**, 107004 (2010); Wei-Guo Yin *et al.*, arXiv:1106.0881.
[18] Weicheng Lv *et al.*, Phys. Rev. B **82**, 045125 (2010).
[19] C.-C. Lee *et al.*, Phys. Rev. Lett. **103**, 267001 (2009).
[20] Weicheng Lv *et al.*, Phys. Rev. B **80**, 224506 (2009).
[21] H. Kontani and S. Onari, Phys. Rev. Lett. **104**, 157001 (2010).
[22] C.-C. Chen *et al.*, Phys. Rev. B **82**, 100504(R) (2010).
[23] S. Raghu *et al.*, Phys. Rev. B **77**, 220503(R) (2008).
[24] Clarence Zener, Phys. Rev. **82**, 403 (1951); P. W. Anderson and H. Hasegawa, *ibid.* **100**, 675 (1955).
[25] Elbio Dagotto *et al.*, Phys. Rep. **344**, 1 (2001).
[26] Lei Hao and Jun Wang, Phys. Rev. B **76**, 134420 (2007).
[27] Ying Ran *et al.*, Phys. Rev. B **79**, 014505 (2009).
[28] Yi Gao *et al.*, Phys. Rev. Lett. **106**, 027004 (2011).
[29] K. Kubo and P. Thalmeier, J. Phys. Soc. Jpn. **78**, 083704 (2009).
[30] Lei Hao and T. K. Lee, Phys. Rev. B **81**, 165445 (2010).
[31] P. A. Bhobe *et al.*, Phys. Rev. Lett. **104**, 236404 (2010).
[32] Yumin Qian *et al.*, New J. Phys. **13**, 053002 (2011).